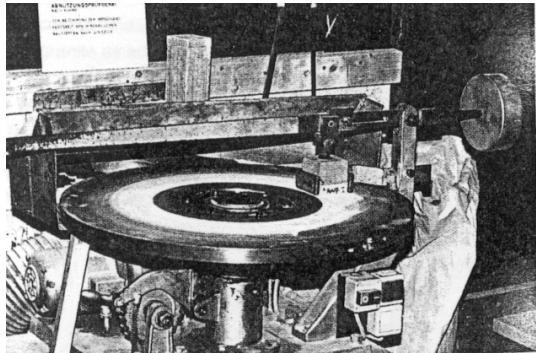
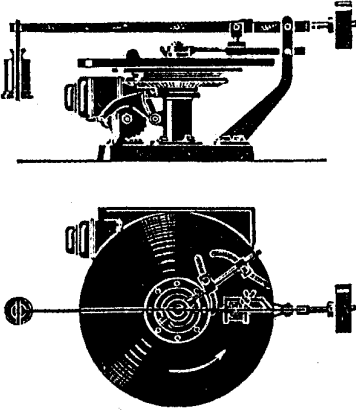


Appendix U.5.5 – SI 6

Generic Name of Test	Sliding Fine Abrasive : Abrasion Test								
Principle of Test	Large revolving steel disc causes abrasive to slide/roll beneath loaded specimens								
Historic Development of Test	The abrasion test in the <i>Israel Standard SI 6-Terrazzo Tiles</i> utilises the Amsler apparatus. The name of this apparatus derives from the Swiss firm Alfred J. Amsler, which built abrasion machines according to the Böhme principle. Böhme's principle is that the sample is held under a certain pressure onto a cast iron disc, rotating in the horizontal plane. An abrading agent is applied to the disc. The loss of thickness is measured after a certain number of rotations of the disc. The number of revolutions is converted into the total wear path. [v.d. Klugt (1989)]								
Apparatus and Abrasives	Figures U.5.5.1 and U.5.5.2 show the apparatus consisting of a horizontally rotating cast iron disk against which the specimen is held. Emery sand is used as an abrasive between the specimen and plate. A simple lever system applies a constant force to the test specimen. [Alexander (1984)]								
 <p data-bbox="266 1262 773 1318">Figure U.5.5.1 Amsler apparatus as used in the SI 6 test. [Pickel (1997)]</p>	 <p data-bbox="943 1289 1317 1373">Figure U.5.5.2 Böhme disc. Note the simple lever system for applying a controlled pressure. [Pickel (1997)]</p>								
Test Method	It is not known if the specimens are tested in an oven dried or wet state. The specimen (71 x 71mm) is held against the rotating grinding disk at a controlled pressure and is turned 90° once during the full test. The emery sand is replaced after every 22 revolutions of the grinding disc. The test duration is either 220 or 440 revolutions depending on the severity of the test required. [Alexander (1984)]								
Abrasion Wear	This is expressed as the average depth of abrasion wear, which is measured as the loss of thickness of the test specimen. [Alexander (1984)]. Ishai (1984) used this test for measuring the abrasion resistance of pavers, and the Israeli standards specify that wear after 440 revolutions should be less than 2.0mm average and less than 2.3mm individual.								
References	<table border="0" style="width: 100%;"> <thead> <tr> <th style="text-align: left;"><u>Author</u></th> <th style="text-align: left;"><u>Comment</u></th> </tr> </thead> <tbody> <tr> <td>Alexander (1984)</td> <td>Source document</td> </tr> <tr> <td>van der Klugt (1989)</td> <td>Source document</td> </tr> <tr> <td>Pickel (1997)</td> <td>Source document</td> </tr> </tbody> </table>	<u>Author</u>	<u>Comment</u>	Alexander (1984)	Source document	van der Klugt (1989)	Source document	Pickel (1997)	Source document
<u>Author</u>	<u>Comment</u>								
Alexander (1984)	Source document								
van der Klugt (1989)	Source document								
Pickel (1997)	Source document								

APPENDIX U.5.5

Wear Mechanisms according to Author

(i) Alexander (1984) The abrading action is that of rubbing and grinding and sliding and cutting of the grit. No high stresses or impacts are applied.

(ii) Visual Effects:

Wear Mechanisms according to writer [R2 S2 I0]

(i) Rolling and Sliding: The mechanism of wear is shown in figure U.5.5.3 and is one of microscopic crushing and shearing at the contact points, as the sand is made to move laterally beneath the specimen. The sand will be made to both slide and roll. The predominant action in the case of sliding will be shearing in the form of scratching, scraping and cutting of the asperities. In the case of rolling, sharp points are likely to generate high compressive stress, resulting in microscopic crushing in very localised areas. The corresponding abrasion wear for the 2 cases may be referred to as:

$$Q_{\text{Crushing}} \propto W_{n+1}$$

$$Q_{\text{Shearing}} \propto F_n = \mu W_n$$

Note: This test does not measure the aggregate/paste bond. The aggregate particles that are loosened during

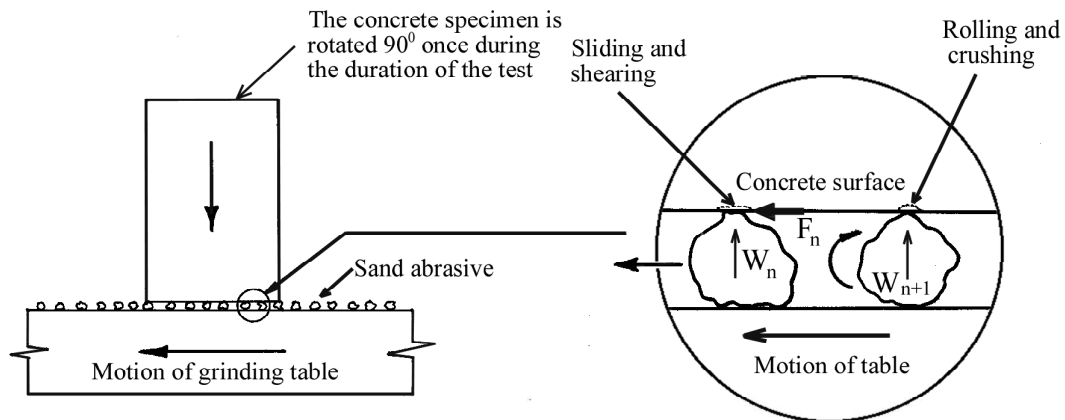


Figure U.5.5.3 Rolling and sliding wear mechanisms

the abrasion process are unable to 'escape'. In effect they contribute to an unrealistically high 'abrasion resistance' result, whereas in practise they would be plucked out of the matrix by traffic etc. The size of loose aggregate that is in effect 'trapped' will depend on the gap between the test sample and the grinding table, and this in turn is determined by the size of the abrasive particles.

(ii) Adhesion and deformation: See note 1 in introduction to appendix U